

Micro-Raman scattering investigation of MgB_2 and RB_2 ($\text{R}=\text{Al}$, Mn , Nb and Ti)

N. Ogita¹, T. Kariya², K. Hiraoka², J. Nagamatsu³, T. Muranaka³, H. Takagiwa³,
J. Akimitsu³ and M. Udagawa¹

¹*Faculty of Integrated Arts and Sciences, Hiroshima University, Hiroshima 739-8521, Japan*

²*Faculty of Engineering, Ehime University, Matsuyama 790-8577, Japan*

³*Department of Physics, Aoyama-Gakuin University, Tokyo 157-8521, Japan*

Abstract

Phonon spectra have been investigated by micro-Raman scattering from 290 to 20K. New peaks at 500 and 674 cm^{-1} appear below 250K in MgB_2 . These peaks are explained by the Fermi resonance, where Raman-active E_{2g} interacts with the overtone of E_{1u} due to anharmonicity. Raman spectra of the isostructural RB_2 ($\text{R}=\text{Al}$, Mn , Nb and Ti) have been also measured at 290K. The line width of E_{2g} phonon of the superconductor MgB_2 and NbB_2 shows the broader than that of the non-superconductors. It is found that the anharmonicity of phonons is important for the superconductivity for MgB_2 .

78.30.-j, 74.25.Kc, 63.20.Kr, 63.20.Ry

Soon after the discovery of high- T_C superconductivity of MgB_2 by Akimitsu and his coworkers¹, it was revealed by the isotope effect by the substitution of ^{11}B ² and the observation of a coherent peak in the NMR experiment³ that MgB_2 is a BCS-type superconductor with the electron-phonon coupling and its symmetry is a s-wave. With increasing the applied pressure, the transition temperature (T_C) decreases^{4,5}, but, this pressure dependence is not explained by the simple BCS theory. Loa and Syassen⁶ explained the pressure depen-

dence of T_C by the combination of increasing phonon frequency and decreasing electronic density of states at Fermi surface. These feature of MgB_2 is related to the layered structure, consisting of the alternating stacking of the hexagonal layer of Mg and the graphite-like layer of B along the c -axis. Some reports emphasize that the layered B state plays the most important role of the appearance of superconductivity.⁷⁻⁹ Thus, the microscopic origin of high- T_C superconductivity in MgB_2 is not fully understood and the important knowledge may be the atomic interaction of inter- and intra-plane.

Raman spectroscopy is an excellent technique to investigate elementary excitation, such as phonons. The $P6/mmm$ symmetry of the MgB_2 structure gives us the following phonon number for each irreducible representations at Brillouion zone center; $\Gamma = 2A_{2u} + B_{1g} + E_{2g} + 2E_{1u}$. The Raman active phonon is only E_{2g} , which is the out-of-phase vibration of the adjacent B atoms in the c -plane. In the Raman scattering, the phonon due to Mg cannot be observed, since Mg locates just on the inversion center.

The Raman scattering spectra of MgB_2 have been reported by several group¹⁰⁻¹². Bohnen *et al.* assigned the broad mode at 580 cm^{-1} to be the E_{2g} mode from the agreement of phonon energies with their lattice dynamical calculation¹⁰. In general, for this crystal structure, the E_{2g} mode should be the highest energy phonon than that of the B_{1g} mode, which is the out of plane mode of B. However, in the actual MgB_2 , the energy of E_{2g} mode is lower than that of B_{1g} due to the strong electron-phonon coupling^{10,13}. Alexander *et al.* also concluded that the E_{2g} phonon is strongly anharmonic and couples to electronic excitations¹¹. Martinho *et al.*, however, concluded from the resonant Raman experiment that the E_{2g} phonon near the Γ point may not play an important role in the electron-phonon coupling for the superconductivity in MgB_2 ¹². Although MgB_2 is the superconductor due to the phonon mechanism, the role of the phonons is still unclear, even the E_{2g} phonon.

In this letter we present the Raman scattering spectra measured by the microscope system, to obtain the pure spectra from the superconducting part, since the sample was polycrystalline. We also studied the other isostructural crystals for the comparison with MgB_2 .

For MgB_2 , we employed three different samples; the commercial one (Rare metallic Co. Japan), the prepared sample by a HIP, and the sample annealed in a high pressure after the HIP preparation. The Raman scattering spectra shown in this report are the spectra from the last annealed sample. Other samples of RB_2 ($\text{R}=\text{Al}$, Mn , Nb , and Ti) were grown by a sintering.

In Raman scattering experiments, the laser beam of 514.5 and 488 nm from an Ar ion laser was employed as an incident light. In the micro-Raman scattering system attached with the $\times 50$ objective, the incident light was focused in a $\sim 2\mu\text{m}$ area in diameter on the sample surface. While, the size of the focused area became $\sim 80\mu\text{m}$ in diameter in the macro-Raman scattering experiments. The scattered light was analyzed by a triple-monochromator (JASCO, NR-1800) and detected by a multichannel CCD detector cooled by a liq. N_2 (Princeton Instruments). In the measurements of the low temperatures, we employed a ^4He -flow type cryostat for both macro- and micro-Raman scattering. To avoid local heating by the incident light, a ^4He heat-exchange gas was filled in the sample cell. The polarization dependence was not measured, since the sample was polycrystalline.

Figure 1 is the photograph of the polished surface of the annealed sample of MgB_2 after the HIP preparation. As shown in Fig.1, three different color grains of gold, blue and black are recognized. The grain size are about $3\sim 5\mu\text{m}$. The dark blue spot at the center of the photograph corresponds to the incident light. The Raman scattering spectra from each grain are shown in Fig.2. Comparing these spectra with our macro-Raman results and reported ones^{10,7,7}, the gold grain is regarded as MgB_2 . The additional peaks observed in other grains are the spectra from the following impurities. The existence of a small amount of MgB_4 , MgB_6 , MgB_{12} , MgO , and MgCO_3 has been observed by the X-ray diffraction.

Figure 3 shows the temperature dependence of the micro-Raman scattering spectra from the gold grain measured with the $\times 50$ objective. Each spectrum is shifted along the vertical axis to avoid crossing. The peaks, labelled by asterisks, are phonons from the blue or black grain. As shown in Fig. 3, new peaks labelled by arrows appear at 500 and 674 cm^{-1} below $T\sim 250\text{K}$. Their energy, line width, and the relative intensity $I(500\text{cm}^{-1})/I(674\text{cm}^{-1})$ do not

depend on temperature. These peaks are originated from the Raman process, since we have obtained the same spectra in the different excitation energy. We note that the intensity of the broad spectra from 400 to 800 cm^{-1} observed at 290K does not grow at the low temperatures.

Figure 4 shows the temperature dependence of the macro-Raman scattering spectra. As shown in Fig. 4, only E_{2g} phonon is observed for all temperatures. At 290K, the spectra are similar with those measured by micro-Raman scattering, because the gold region is dominant on the sample surface. In this macro-Raman spectra, the intensity of E_{2g} increases at the lower temperatures. In addition, the new peaks have not been observed. Therefore, the spectra of the macro-Raman spectra become different from the micro-one below $T \simeq 250\text{K}$.

To check this spectral difference between the micro- and macro-Raman scattering in $T < 250\text{K}$, we changed the magnification ratio of the objectives. New peaks cannot be observed for the larger spot size of the incident beam than the grain size of $5\mu\text{m}$. We have not observed the new peaks for the commercial and the HIP-prepared samples, where the grain size of the gold part is much less than $1\mu\text{m}$. Thus, the grain size at the focused area is important to observed the new peaks.

The inset of Fig. 4 shows the temperature dependence of the energy and line width of the E_{2g} phonon. The line width is shown by vertical solid bar. In the temperature region above $T \simeq 250\text{K}$, the peak energy increases with decreasing temperature, while below $T \simeq 250\text{K}$ the energy is almost constant. The solid line shows the estimated phonon energy from the reported Grüneisen parameter ($\gamma = d\ln\nu/3d\ln a = 3.9$)¹¹ and lattice constants¹⁴. As shown in the inset of Fig. 4, the temperature dependence of the E_{2g} phonon energy is explained by the ordinary thermal expansion for $T < 250\text{K}$, but the deviation of the observed energy from the estimated energy is clearly seen for $T > 250\text{K}$.

Here we summarize the experimental results of the temperature dependence of MgB_2 . We have found the characteristic temperature $T \simeq 250\text{K}$ in MgB_2 , where the new peaks appear in micro-measurement and also the temperature dependence of E_{2g} phonon energy deviates from the expected energy of the thermal expansion. Furthermore, the appearance of the

new peaks is related to phonon coherence, because this depends on the spacial length ratio between the grain size and the laser spot size.

Next, we discuss about the new peaks at 500 and 674 cm^{-1} observed in micro-measurement for $T < 250\text{K}$. The two peaks cannot be assigned as the first order phonon, because of no structural change. As shown in Fig. 4, the E_{2g} phonon intensity becomes large with decreasing temperature in the macro-measurement. If we apply this temperature dependence of the macro-one to the micro-case, the spectrum should be observed at low temperature, as shown by (a) in Fig. 3. However, only two peaks are observed in the actual spectra without the increase of the back ground intensity. This fact suggests that the intensity of E_{2g} transfers to the new peaks below $T \simeq 250\text{K}$. In addition, the E_{2g} phonon is observed at nearly center of the two peaks as shown in Fig. 3. Therefore, these intensity transfer and energy distribution show the existence of the coupling between E_{2g} and the others.

The coupled modes with E_{2g} should be the well defined mode, since the line width of the new peaks is too narrow. From this point of view, the electronic case is excluded, since its line width might be broad. Thus, the possible excitation in this crystal is phonon.

The coupling mode should satisfy the following conditions; (1)*the same symmetry representation* of E_{2g} and (2)*the close energy to E_{2g} phonon*. In the first order process, we cannot find such phonons. Then, the plausible mode is the overtone of E_{1u} , because the E_{1u} mode is also in-plane vibration of B as same as E_{2g} mode. In fact, the overtone modes of E_{1u} includes the symmetry of E_{2g} from $E_{1u} \times E_{1u} = A_{1g} + E_{1u} + E_{2g}$ and its twice of energy is very close to that of the E_{2g} phonon, because the calculated energies of E_{1u} phonon are 250-300 cm^{-1} and 322 cm^{-1} at Brillouin zone boundary and center¹⁰, respectively. As the coupling between the overtone mode and one phonon, Fermi resonance is known¹⁵.

The detailed procedure of the Fermi resonance is represented in Ref.¹⁶. The Fermi coupling constant (K), bare phonon energy of E_{2g} (Ω_1) and that of the overtone E_{1u} ($2\Omega_2$) are described by

$$\begin{aligned}
K &= \sqrt{2}[\Omega_+ - \Omega_-] \frac{(1 - RR_0)(R + R_0)}{(1 - RR_0)^2 + (R + R_0)^2} \\
\Omega_1 &= \frac{1}{2}[\Omega_+ + \Omega_-] - \frac{1}{2}\sqrt{(\Omega_+ - \Omega_-)^2 - 2K^2} \\
2\Omega_2 &= \frac{1}{2}[\Omega_+ + \Omega_-] + \frac{1}{2}\sqrt{(\Omega_+ - \Omega_-)^2 - 2K^2},
\end{aligned}$$

where R and R_0 are the ratio of the Raman polarizability matrix elements for the resonated case and the uncoupled one ($R=\alpha_{0-}/\alpha_{0+}$ and $R_0=\alpha_{02}/\alpha_{01}$), respectively. Ω_+ and Ω_- are the frequencies in the resonance. In the above equations, the observed parameters are Ω_+ and Ω_- , and R^2 which corresponds to the intensity ratio $I(\Omega_-)/I(\Omega_+)$. While the unknown parameters are R_0 , K , Ω_1 and Ω_2 . In this analysis, we assume $\Omega_1=620\text{cm}^{-1}$ because the E_{2g} mode observed by the macro-measurements does not show any coupling in all temperatures as shown in Fig.4. Then, using the observed values of $\Omega_+=674\text{ cm}^{-1}$, $\Omega_-=500\text{ cm}^{-1}$, $R=2.41$ and $\Omega_1=620\text{ cm}^{-1}$, we obtain the Fermi coupling constant $K\simeq 114$ and bare overtone frequency $2\Omega_2=554\text{cm}^{-1}$ for both two solutions of $R_0=1.51$ and 5 . The energy agrees with the reported value of E_{1u} phonon at Brillouin zone boundary¹⁰.

As the extension of the above discussion, we comment on the origin of the high temperature superconductivity in MgB_2 . The mediated phonons in the mechanism of superconductivity are probably the E_{1u} phonon, because the E_{1u} phonons include the in-plane motion of borons. When the E_{1u} phonons couple with E_{2g} phonons, an effective phonon frequency increases. As the result, the T_C increases. This consideration is not discrepant with the results by Martinho *et al.*, where the E_{2g} phonon did not show the expected spectral change at T_C , because the E_{2g} phonon plays indirectly to the superconducting mechanism.

Finally, we present the results for the reference materials of RB_2 ($R=\text{Al, Mn, Nb, Ti and Y}$), where the Raman-active phonon is only E_{2g} . Among the materials, MgB_2 and NbB_2 ($T_C=5\text{K}$) shows superconductivity. Figure 5 shows the plot of the phonon energy and line width as a function of the ratio of lattice constants (c/a). The line width is presented by the vertical bar. As shown in Fig. 5, the E_{2g} phonon frequency decreases with increasing ratio of c/a . Most pronounced property is the line width, since that of the superconducting crystals of MgB_2 and NbB_2 has the broader line width, compared with the others. This suggests

that the large anharmonicity of phonons is necessary for the appearance of superconductivity in RB_2 structure. Furthermore, the increase of c/a corresponds to the increase of the two-dimensional character and the decrease of the inter-layer interaction. It can be seen from the figure that the ratio seems to be proportional to T_C . Thus, to obtain the higher- T_C crystals, we should seek the crystals with the larger c/a and the weaker interlayer-interaction between the cation R and B. In addition, there remains the problem, whether such two dimensional character in MgB_2 is similar to that of the oxide superconductors of Sr_2RuO_4 ¹⁷ or not.

This work is supported in part by a Grant-in-Aid for COE Research (No.13CE2002) of the Ministry of Education, Culture, Sports, Science and Technology of Japan. The low temperature experiments was also supported by the cryogenic center of Hiroshima University.

REFERENCES

1. J. Nagamatsu, *et al.*, Nature **410**, 63 (2001).
2. S. L. Bud'ko, *et al.*, Phys. Rev. Lett. **86**, 1877 (2001).
3. H. Kotegawa, *et al.*, (cond-mat/0102334).
4. B. Lorenz, R. L. Meng, and C. W. Chu, (con-mat/0102246).
5. M. Monteverde, *et. al*, Science inpress.
6. I. Loa and Syassen, (cond-mat/0102462) Sold State Commun., In press.
7. J. M. C. An and W. E. Pickett, Phys. Rev. Lett. **86**, 4366 (2001).
8. J. Kortus, *et al.*, Phys. Rev. Lett. **86**, 4656 (2001).
9. K. D. Belashenko, *et al.*, cond-mat/0102290(2001).
10. K. -P. Bohnen, *et al.*,(cond-mat/0103319).
11. Alexander, F. Goncharov *et.al*, (cond-mat/0104042).
12. H. Martinho *et.al*, (cond-mat/0105204).
13. M. Shirai, private communication.
14. J. D. Jorgensen, *et al.*, (cond-mat/0103069).
15. F. Fermi, Zeits. f. Physik. **71**, 250 (1931).
16. A. Hacura, *et al.*, J. Mol. Struct. **218**, 297 (1990).
17. S. Sakita, *et al.*, Phys. Rev. **63**, 134520 (2001)

This figure "figure1.jpg" is available in "jpg" format from:

<http://arXiv.org/ps/cond-mat/0106147v1>

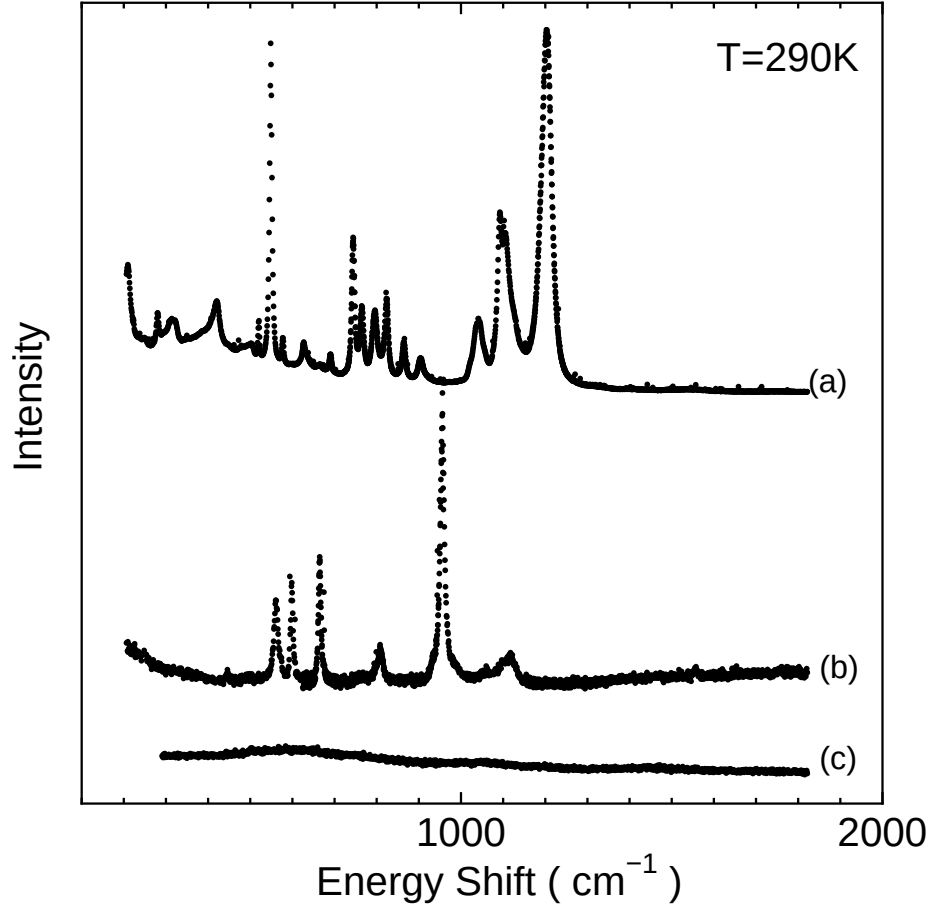


Fig. 2: (a) Raman scattering spectrum from black grain(a), blue(b) and gold(c) measured by the micro-Raman spectra with the $\times 50$ objective at 290K. The (c) is the Raman scattering spectrum of MgB_2 .

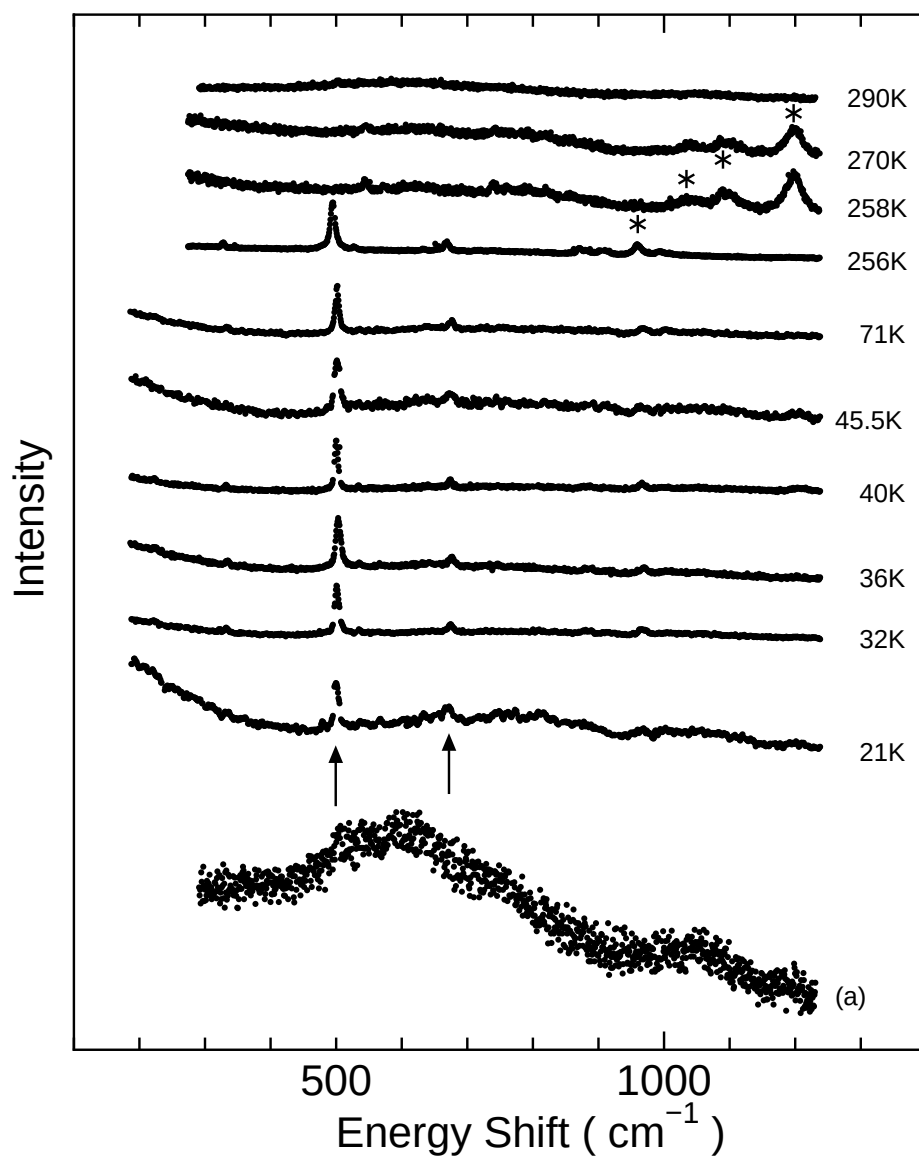


Fig. 3: Temperature dependence of micro-Raman spectra from the gold grain. Arrows denote the new peaks and astarisks are the phonons from the blue and black grains. The spectrum (a) is the magnified spectrum of 290K by ten times.

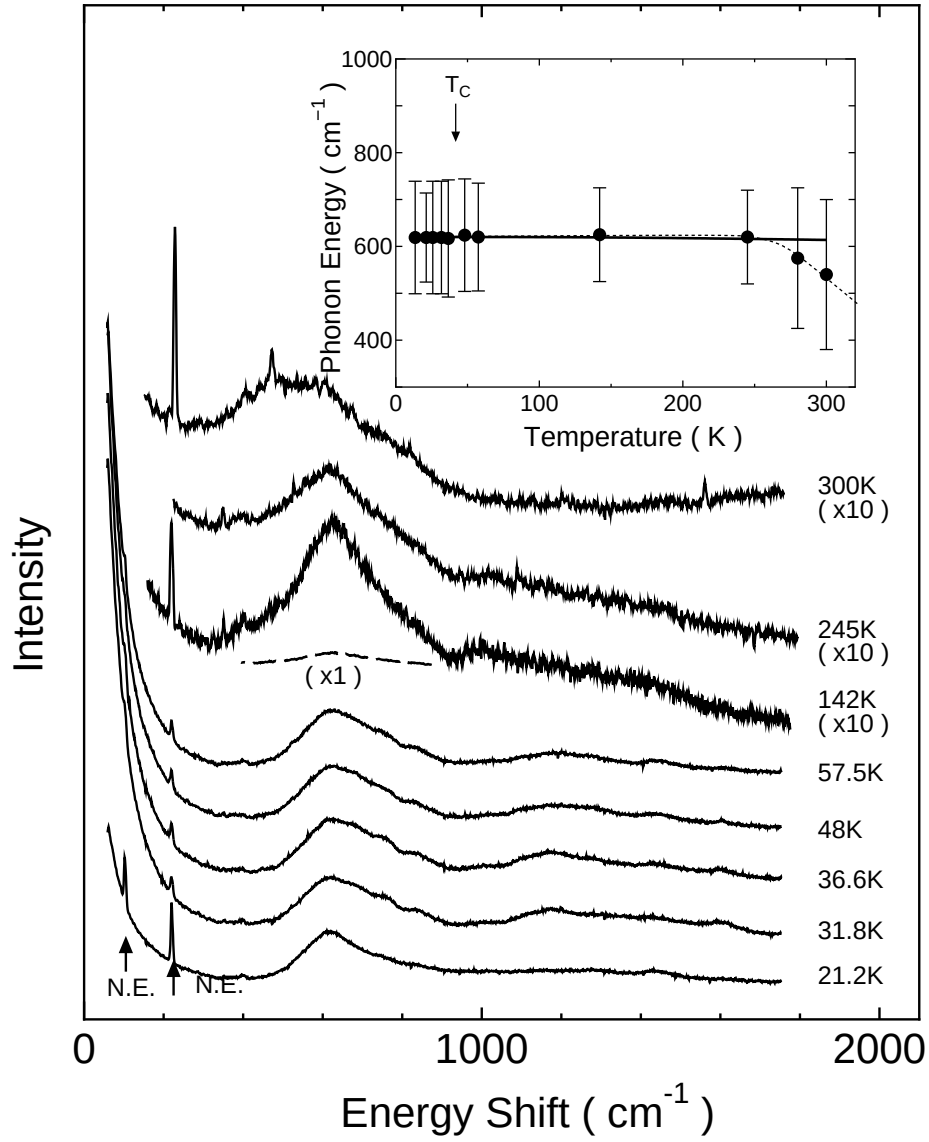


Fig. 4: Temperature dependence of macro-Raman spectra. The inset shows the dependence of phonon energy and the width of E_{2g} . The solid line is estimated phonon energy derived from Ref. [11,14]. The dotted line is a guide for eyes.

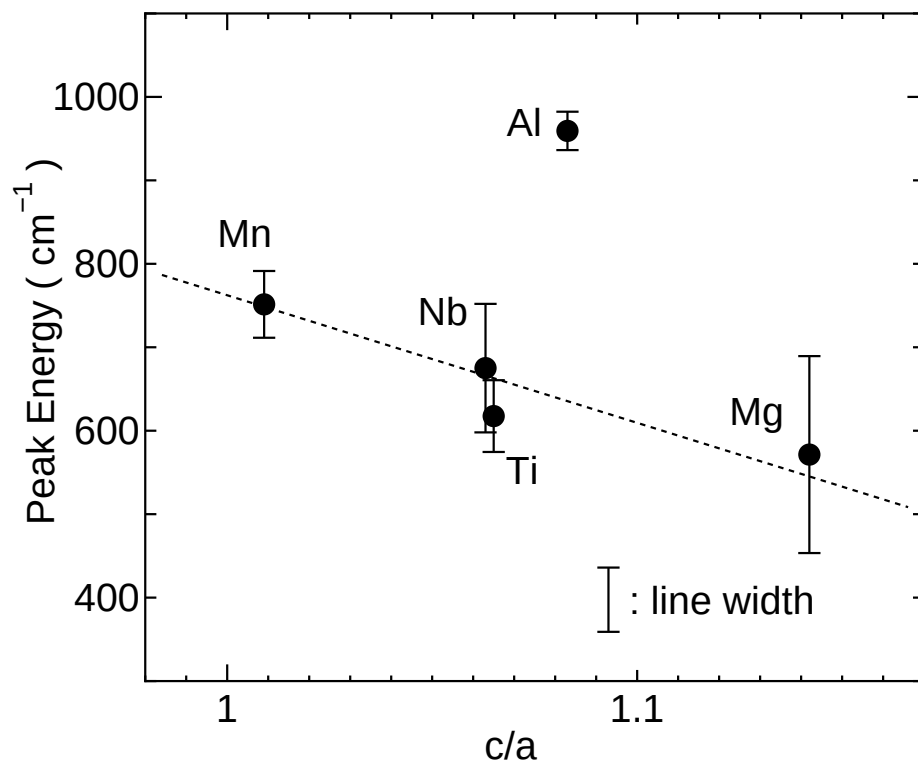


Fig. 5: E_{2g} phonon energy and line width vs. the ratio of lattice constant c/a . The dotted line is guid for eyes.